

Spectroscopic Studies on ZrO₂ Modified with MoO₃ and Activity for Acid Catalysis

Jong Rack Sohn,* Eun Woo Chun, and Young Il Pae[†]

Department of Industrial Chemistry, Engineering College, Kyungpook National University, Daegu 702-701, Korea

[†]Department of Chemistry, University of Ulsan, Ulsan 680-749, Korea

Received August 1, 2003

Zirconia modified with MoO₃ was prepared by impregnation of powdered Zr(OH)₄ with ammonium heptamolybdate aqueous solution followed by calcining in air at high temperature. Spectroscopic studies on prepared catalysts were performed by using FTIR, Raman, XRD, and DSC and by measuring surface area. Upon the addition of molybdenum oxide to zirconia up to 15 wt%, the specific surface area increased in proportion to the molybdate oxide content, while acidity measured by irreversible chemisorption of ammonia exhibited a maximum value at 3 wt% of MoO₃. Since the ZrO₂ stabilizes the molybdenum oxide species, for the samples equal to or less than 30 wt%, molybdenum oxide was well dispersed on the surface of zirconia and no phase of crystalline MoO₃ was observed at any calcination temperature above 400 °C. The catalytic activities for cumene dealkylation were roughly correlated with the acidity of catalysts measured by ammonia chemisorption method, while the catalytic activities for 2-propanol dehydration were not correlated with the acidity because weak acid sites are necessary for the reaction.

Key Words : MoO₃/ZrO₂ catalyst, Spectroscopic characterization, Acid catalysis, 2-Propanol dehydration, Cumene dealkylation

Introduction

Supported molybdenum oxide catalysts are extremely important for industrial applications. These systems are active for various reactions, such as partial oxidation of hydrocarbons and alcohols,¹⁻⁵ hydrogenolysis and hydrodesulfurization of crude oil,^{6,7} metathesis of alkenes,⁸ hydrogenation of benzene,⁹ and cracking of hydrocarbons.¹⁰ The conventional way to prepare the catalysts is to impregnate the high surface area support oxide with an aqueous solution of ammonium heptamolybdate followed by calcining the solid in air. Usually the supports are alumina or silica, but considerable interest is now devoted to other supports such as TiO₂,¹¹ Nb₂O₅,¹² and ZrO₂.^{6,10,13-15} Zirconia is a very interesting material because of its thermal stability, its mechanical properties, and its basic, acidic, reducing, and oxidizing surface properties. Therefore, it is attracting interest in catalysis as a support material as well as a catalyst.

It has been reported by several workers that the addition of platinum to zirconia modified by sulfate ions enhances catalytic activity in the skeletal isomerization of alkanes without deactivation when the reaction is carried out in the presence of hydrogen.^{16,17} The high catalytic activity and small deactivation can be explained by both the elimination of the coke by hydrogenation and hydrogenolysis and the formation of Brønsted acid sites from H₂ on the catalysts.¹⁶ Recently, Arata¹⁸ reported zirconia-supported molybdenum oxide as an alternative material in reaction requiring strong acid sites. Several advantages of molybdate, over sulfate, as dopant include that it does not suffer from dopant loss during

thermal treatment and it undergoes significantly less deactivation during catalytic reaction. So far, however, supported molybdenum oxide catalysts have been mainly on alumina¹⁹ and silica,²⁰ and only some work was studied for the ZrO₂ support.¹³⁻¹⁵ Moreover, there is no systematic study using a variety of instruments, although some limited work by Raman spectroscopy and X-ray diffraction was reported.¹³⁻¹⁵

This paper describes spectroscopic studies on ZrO₂ modified with MoO₃ and catalytic activity for acid catalysis. The spectroscopic studies of the samples were performed by means of Fourier transform infrared (FTIR), X-ray diffraction (XRD), laser Raman, Differential scanning calorimetry (DSC), and by the measurement of surface area.

Experimental Section

The precipitate of Zr(OH)₄ was obtained by adding aqueous ammonia slowly into an aqueous solution of zirconium oxichloride (Aldrich) at room temperature with stirring until the pH of aqueous solution reached about 8.²¹⁻²³ The precipitate was washed thoroughly with distilled water until chloride ion was not detected with AgNO₃ solution, and was dried at room temperature for 12 h. The dried precipitate was powdered (100 mesh) by grinding.

The catalysts containing various molybdenum oxide contents were prepared by adding an aqueous solution of ammonium heptamolybdate[(NH₄)₆(Mo₇O₂₄)·4H₂O] (Aldrich) to the Zr(OH)₄ powder followed by drying and calcining at high temperatures for 3 hr in air. This series of catalysts are denoted by their weight percentage of MoO₃ and calcination temperature. For example, 10-MoO₃/ZrO₂(500) indicates the catalyst containing 10 wt% MoO₃ and calcined at 500 °C for 3 hr.

FTIR spectra were obtained in a heatable gas cell at room

*To whom all correspondences should be addressed. Tel: +82-53-950-5585, e-mail: jrsohn@knu.ac.kr

temperature using Mattson Model GL6030E spectrophotometer. The wafers contained about 9 mg/cm² self-supporting catalyst. Prior to obtaining the spectra, the samples were heated under vacuum at 400-500 °C for 1.5 hr.

The Raman spectra were obtained with a Spex Ramalog spectrometer with holographic gratings. The 5145-Å line from a Spectra-Physics Model 165 argon-ion laser was used as the exciting source. The laser beam was focussed onto an area 0.1 × 0.1 mm² in size of the sample surface; a 90° scattering geometry was used. The spectral shift width was typically 4 cm⁻¹, and laser source powers of approximately 45 mW, measured at the sample, were used.

Catalysts were checked in order to determine the structure of the support as well as that of molybdenum oxide by means of a Jeol Model JDX-8030 diffractometer, employing Ni-filtered Cu K_α radiation.

DSC measurements were performed by a PL-STA model 1500H apparatus in air, and the heating rate was 5 °C per minute. For each experiment 10-15 mg of sample was used.

The acid strength of catalyst was measured qualitatively using a series of the Hammett indicators.^{24,25} The catalyst in a glass tube was pretreated at 400 °C for 1 hr and filled with dry nitrogen. For the determination of acid strength of the catalyst the color changes of indicators were observed by spot test. Chemisorption of ammonia was employed as a measure of acidity of catalysts. The amount of chemisorption was obtained as the irreversible adsorption of ammonia.^{26,27} Thus the first adsorption of ammonia at 20 °C and 300 torr was followed by evacuation at 230 °C for 1 hr and re-adsorption at 20 °C, the difference between two adsorptions at 20 °C giving the amount of chemisorption. The specific surface area was determined by applying the BET method to the adsorption of nitrogen at -196 °C.

2-propanol dehydration was carried at 160 and 180 °C in a pulse micro-reactor connected to a gas chromatograph. Fresh catalyst in the reactor made of 1/4 inch stainless steel was pretreated at 400 °C for 1 hr in the nitrogen atmosphere. Diethyleneglycol succinate on Simalite was used as packing material of gas chromatograph and the column temperature was 180 °C for analyzing the product. Catalytic activity for 2-propanol dehydration was represented as mole of propylene converted from 2-propanol per gram of catalyst. Cumene dealkylation was carried out at 400 and 450 °C in the same reactor as above. Packing material for the gas chromatograph was Benton 34 on chromosorb W and column temperature was 130 °C. Catalytic activity for cumene dealkylation was represented as mole of benzene converted from cumene per gram of catalyst. Conversion for both reactions were taken as the average of the first to sixth pulse values.

Results and Discussion

Raman and Infrared Spectra. Raman spectroscopy is a valuable tool for the characterization of dispersed metal oxides and detects vibrational modes of surface and bulk structures. The Raman spectra of MoO₃ obtained by

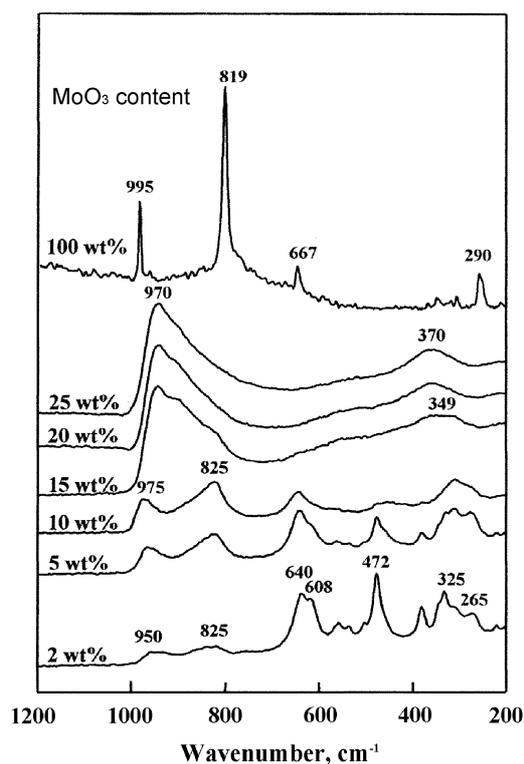


Figure 1. Raman spectra of MoO₃/ZrO₂(500).

calcining ammonium heptamolybdate at 500 °C, MoO₃/ZrO₂ (500), and ZrO₂ under ambient conditions are presented in Figure 1. The MoO₃ structure is made up of distorted MoO₃ octahedra. Bulk MoO₃ shows the main bands, in good agreement with data previously reported.²⁸ The major vibrational modes of MoO₃ are located at 995, 819, 667, and 290 cm⁻¹, and have been assigned to the Mo=O stretching mode, the Mo-O-Mo stretching mode, OMo₃ vibration mode, and the Mo=O deformation mode, respectively.²⁸

The molecular structure of the supported molybdenum oxide species depends on the loading. Several authors observed that the nature of surface molybdenum species on SiO₂, Al₂O₃, TiO₂ and ZrO₂ depends on the amount of MoO₃. A band at about 825 cm⁻¹, corresponding to Mo-O-Mo vibrations,^{29,30} and a band at 910-980 cm⁻¹, assigned to M=O vibrations in two dimensional polymolybdate, were observed in these samples.^{29,30} Raman bands between 910 and 980 cm⁻¹ are usually attributed to the Mo=O vibration of Mo species in either octahedral or tetrahedral environment.³¹ Generally, monomolybdate or tetrahedral molybdenum oxygen species have been assigned for low MoO₃ loading samples,^{29,31,32} and two-dimensional polymolybdates or octahedral molybdenum-oxygen species with characteristic band around 950-980 cm⁻¹, for high MoO₃ loading samples.^{29,31,32} Therefore, the broad band observed in the 900-1000 cm⁻¹ region in Figure 1 will be interpreted as an overlap of two characteristic bands for two molybdenum oxide species. The bands around 370 cm⁻¹ for 15-MoO₃/ZrO₂, 20-MoO₃/ZrO₂, and 25-MoO₃/ZrO₂ samples are assigned to Mo=O bending mode.³³

For 15-MoO₃/ZrO₂(500), 20-MoO₃/ZrO₂(500) and 25-

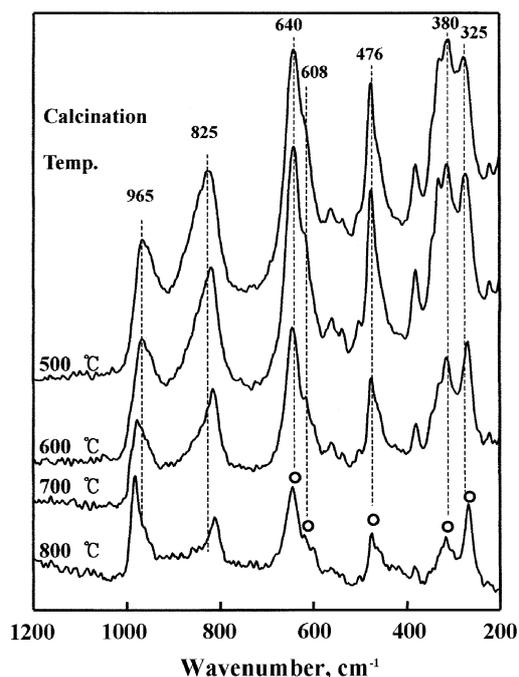


Figure 2. Raman spectra of 5- MoO_3/ZrO_2 calcined at different temperatures: ○, tetragonal phase of ZrO_2 .

$MoO_3/ZrO_2(500)$ in Figure 1, most of zirconia is amorphous to X-ray diffraction, showing tiny amount of tetragonal phase zirconia for the other. The Raman spectrum of amorphous zirconia is characterized by a very weak and broad band at 550-600 cm^{-1} .⁴⁴ Tetragonal zirconia is expected to yield a spectrum consisting of Raman bands with frequencies at about 148, 263, 325, 472, 608, and 640 cm^{-1} , while monoclinic zirconia exhibits the characteristic features at 180, 188, 221, 380, 476, and 637 cm^{-1} .^{35,36} As shown in Figure 1, the 2- MoO_3/ZrO_2 , 5- MoO_3/ZrO_2 , and 10- MoO_3/ZrO_2 samples exhibit the characteristic features of tetragonal zirconia, indicating no transformation of ZrO_2 from tetragonal to monoclinic.

Figure 2 shows Raman spectra of 5- MoO_3/ZrO_2 samples calcined at 500-800 °C for 3 hr. For all samples, a band around 825 cm^{-1} , corresponding to Mo-O-Mo vibrations,^{29,30} and a band around 965 cm^{-1} , assigned to Mo=O vibrations^{29,30} in two dimensional polymolybdate, were observed similarly to those of Figure 1. All samples also exhibit the characteristic features of tetragonal zirconia at 265, 325, 472, 608, and 640 cm^{-1} , in good agreement with XRD data described later.

Figure 3 shows Raman spectra of 15- MoO_3/ZrO_2 samples calcined at 400-900 °C for 3 hr. For samples calcined 400-800 °C, a band around 825 cm^{-1} and a band around 965 cm^{-1} were observed similarly to those of Figures 1 and 2. The samples also exhibit the characteristic features of tetragonal zirconia at 500-800 °C. However, the sample calcined at 900 °C exhibit the characteristic features of monoclinic zirconia, indicating the phase transition of ZrO_2 from tetragonal to monoclinic. From calcination temperature of 700 °C, a new species, *i.e.*, $Zr(MoO_4)_2$ phase, identified by its characteristic

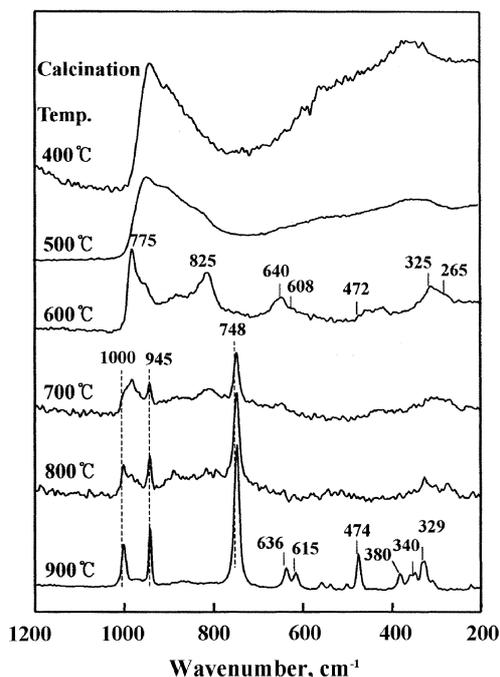


Figure 3. Raman spectra of 15- MoO_3/ZrO_2 calcined at different temperatures.

Raman bands²⁹ at 748, 944, and 1000 cm^{-1} , has been detected in the 15- MoO_3/ZrO_2 catalyst. As shown in Figure 3, the amount of $Zr(MoO_4)_2$ phase increased with the calcination temperature. Chen *et al.*¹⁵ reported the formation of $Zr(MoO_4)_2$ from MoO_3 and ZrO_2 in high loading sample

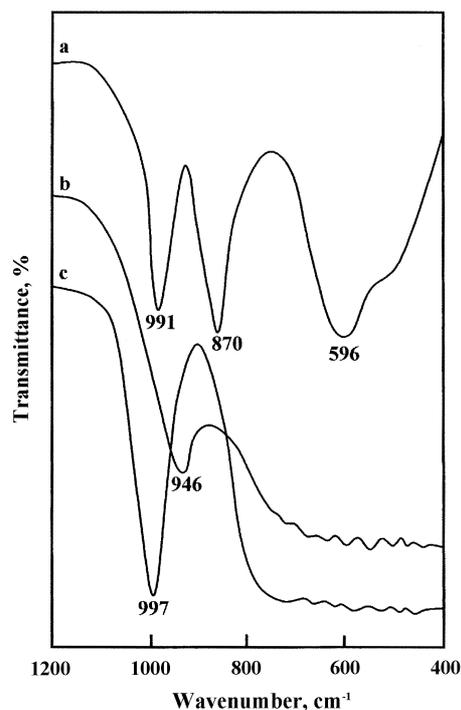


Figure 4. Infrared spectra of (a) bulk MoO_3 , (b) 15- $MoO_3/ZrO_2(500)$ evacuated at 25 °C, and (c) 15- $MoO_3/ZrO_2(500)$ evacuated at 500 °C.

calcined above 600 °C.

The Raman spectra in Figures 1-3 have been taken in air using the pure powders. To examine the structure of ZrO₂ modified with MoO₃ under dehydration conditions, IR spectra of 15-MoO₃/ZrO₂ sample were obtained in a heatable gas cell after evacuation at 298 and 773 K for 1.5 h. The IR spectrum for bulk MoO₃ is also presented for the range, 1200-400 cm⁻¹ in Figure 4. In view of Raman spectrum of bulk MoO₃ in Figure 1, for bulk MoO₃, the IR bands at 991, 870, and 596 cm⁻¹ in Figure 4(a) are assigned to the Mo=O stretching mode, the Mo-O-Mo stretching mode, and OMo₃ vibration mode, respectively. For 15-MoO₃/ZrO₂ sample, IR band at 997 cm⁻¹ after evacuation at 773K is due to the Mo=O stretching mode of the molybdenum oxide complex bonded to the ZrO₂ surface.³⁷ As shown in Figure 4, this Mo=O band due to molybdenyl species only appears on evacuated sample, being shifted on wet sample. The broad band at 946 cm⁻¹ under ambient condition [Figure 4(b)] is assigned to the terminal Mo=O stretching of the hydrated form of the surface molybdenyl species.³⁷ This can be rationalized by assuming that the adsorption of water causes a strong perturbation of the corresponding molybdenum oxide species, with a consequent strong broadening and shift down of this band. This isolated molybdenum oxides species is stabilized through multiple Mo-O-Zr bonds between each molybdenum oxide species and the zirconia surface.^{15,29} Upon dehydration at elevated temperature, the hydrated surface metal oxide species is unstable and decompose to form dehydrated surface metal oxide species by direct interaction with the surface OH groups of support, giving the formation of metal-oxygen-

support bond.³⁸

Crystalline structures of catalysts. The crystalline structures of ZrO₂ and MoO₃/ZrO₂ calcined in air at different temperatures for 3 hr were examined. For pure ZrO₂, ZrO₂ was amorphous to X-ray diffraction up to 300 °C, with a two-phase mixture of the tetragonal and monoclinic forms at 400-700 °C and a monoclinic form at 800 °C (This figure is not shown here). Three crystal structures of ZrO₂, tetragonal, monoclinic and cubic phases have been reported.^{39,40}

However, in the case of ZrO₂ modified with MoO₃, the crystalline structures of the samples were different from that of pure ZrO₂. For the 5-MoO₃/ZrO₂, as shown in Figure 5, X-ray diffraction data indicated tetragonal ZrO₂ form at 400-600 °C, and a two-phase mixture of the tetragonal and monoclinic ZrO₂ forms at 700-900 °C. It is assumed that the interaction between molybdenum oxide and ZrO₂ hinders the transition of ZrO₂ from amorphous to tetragonal phase.^{21,24} The presence of molybdenum oxide strongly influences the development of textural properties with temperature. No phase of molybdenum oxide was observed at any calcination temperature, indicating a good dispersion of molybdenum oxide on the surface of ZrO₂ support due to the interaction between them. Moreover, for the sample of 15-MoO₃/ZrO₂, the transition temperature from the amorphous to the tetragonal phase was higher by 100 K than that of pure ZrO₂. That is, the more the content of molybdenum oxide, the higher the phase transition temperature. As shown in Figure 7, for 15-MoO₃/ZrO₂, ZrO₂ was amorphous to X-ray diffraction up to 400 °C, with a tetragonal phase of ZrO₂ at 500-700 °C, and a two-phase mixture of the tetragonal and monoclinic ZrO₂ forms at 800-900 °C.

XRD patterns of MoO₃-ZrO₂ containing different MoO₃

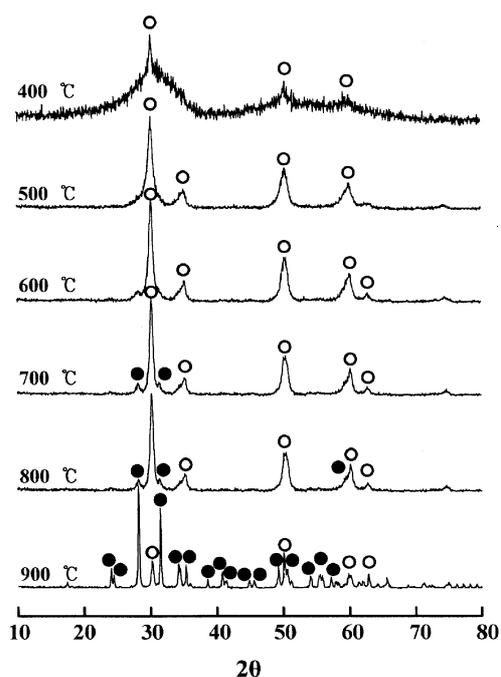


Figure 5. X-ray diffraction patterns of 5-MoO₃/ZrO₂ calcined at different temperatures for 3 hr.: ○, tetragonal phase of ZrO₂; ●, monoclinic phase of ZrO₂.

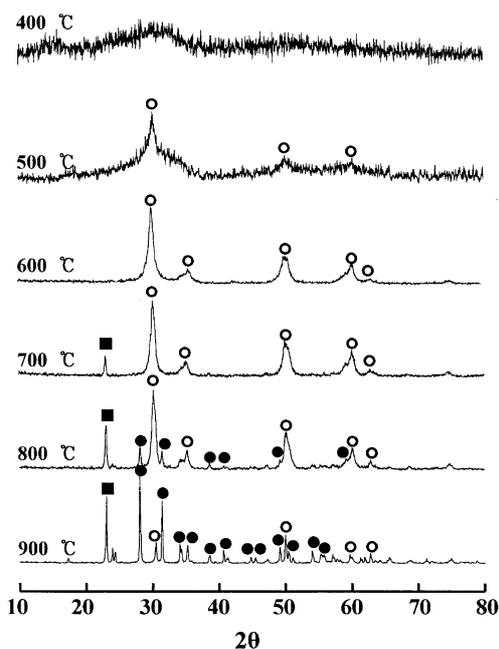


Figure 6. X-ray diffraction patterns of 15-MoO₃/ZrO₂ calcined at different temperatures for 3 hr.: ○, tetragonal phase of ZrO₂; ●, monoclinic phase of ZrO₂; ■, Zr(MoO₄)₂ phase.

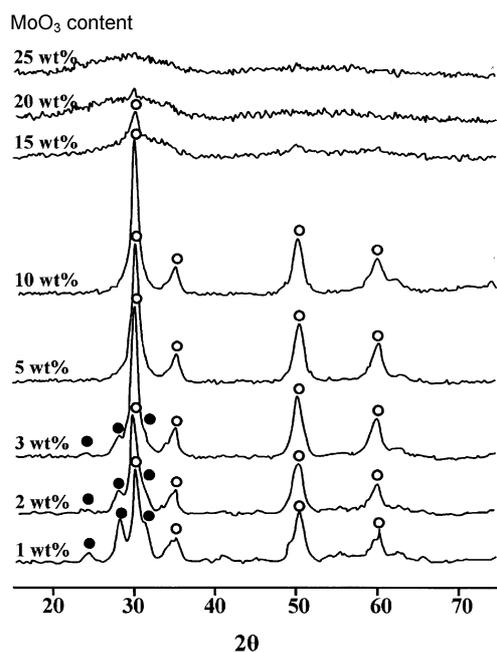


Figure 7. X-ray diffraction patterns of MoO₃-ZrO₂ containing different MoO₃ contents and calcined at 500 °C for 3 hr: ○, tetragonal phase of ZrO₂; ●, monoclinic phase of ZrO₂.

contents and calcined at 500 °C for 3 hr are shown in Figure 7. ZrO₂ is a two-phase mixture of the tetragonal and monoclinic forms up to 3 wt%, but for sample containing MoO₃ equal to or above 15 wt%, ZrO₂ was amorphous because the interaction between MoO₃ and ZrO₂ hinders the phase transition of ZrO₂ from amorphous to tetragonal phase.^{21,24}

It is also of interest to examine the influence of molybdenum oxide on the transition temperature of ZrO₂ from tetragonal to monoclinic phase. In view of X-ray diffraction patterns, the calcination temperatures at which monoclinic phase is observed initially are 500 °C for pure ZrO₂, 700 °C for 5-MoO₃/ZrO₂, 800 °C for 15-MoO₃/ZrO₂, respectively. That is, the transition temperature increases with increasing molybdenum oxide content. This can be also explained in terms of the delay of transition from tetragonal to monoclinic phase due to the interaction between molybdenum oxide and zirconia, in analogy with the delay of transition from amorphous to tetragonal phase described above. For 15-MoO₃/ZrO₂, the XRD patterns clearly show the formation of Zr(MoO₄)₂ from MoO₃ and ZrO₂ at 700-900 °C, showing the increased amount of Zr(MoO₄)₂ phase with the calcination temperature. These results are in good agreement with those of Raman spectra in Figure 3.

Thermal Analysis. In X-ray diffraction pattern, it was shown that the structure of MoO₃/TiO₂ was different depending on the calcined temperature. To examine the thermal properties for the precursors of samples more clearly, their thermal analysis was carried out and illustrated in Figure 8. For pure ZrO₂ the DSC curve showed a broad endothermic peak below 180 °C due to the elimination of adsorbed water, and an exothermic peak at 430 °C due to the

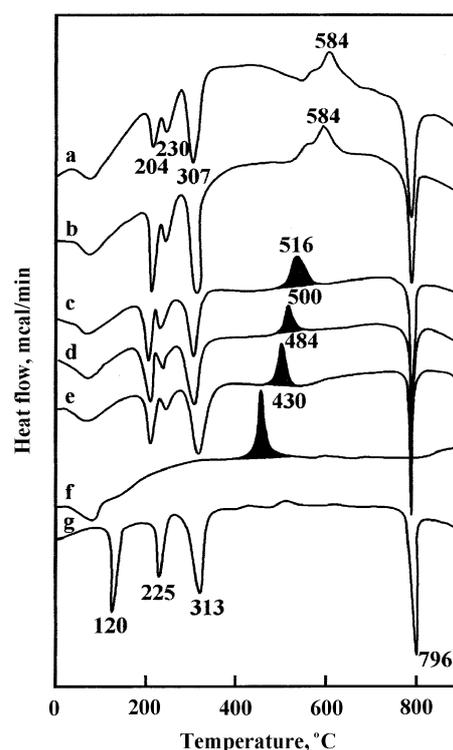


Figure 8. DSC curves of precursors of catalysts: (a) 25-MoO₃/ZrO₂, (b) 15-MoO₃/ZrO₂, (c) 10-MoO₃/ZrO₂, (d) 5-MoO₃/ZrO₂, (e) 1-MoO₃/ZrO₂, (f) ZrO₂, and (g) (NH₄)₆(Mo₇O₂₄)·4H₂O.

ZrO₂ crystallization.^{24,35} In the case of MoO₃/ZrO₂, three additional endothermic peaks appeared in the region of 200-400 °C due to the evolution of NH₃ and H₂O decomposed from ammonium heptamolybdate. Also it is considered that an endothermic at 796 °C is responsible for melting of MoO₃ and an exothermic peaks around 584 °C is due to the formation of Zr(MoO₄)₂ described in X-ray diffraction patterns. However, it is of interest to see the influence of MoO₃ on the crystallization of ZrO₂ from amorphous to tetragonal phase. As Figure 8 shows, the exothermic peak due to the crystallization appears at 430 °C for pure ZrO₂, while for MoO₃/ZrO₂, it was shifted to higher temperatures. The shift increased with increasing MoO₃ content up to 10 wt% of MoO₃. It is considered that the interaction between MoO₃

Table 1. Specific surface area and acidity of MoO₃/ZrO₂ catalysts calcined at 500 °C for 3 hr

Catalyst	Surface area (m ² /g)	Acidity (μmol/g)
ZrO ₂	58	45
1-MoO ₃ /ZrO ₂	111	159.3
2-MoO ₃ /ZrO ₂	113	161.5
3-MoO ₃ /ZrO ₂	121	167.1
5-MoO ₃ /ZrO ₂	135	137.9
10-MoO ₃ /ZrO ₂	171	127.6
15-MoO ₃ /ZrO ₂	193	120.11
20-MoO ₃ /ZrO ₂	188	113.7
25-MoO ₃ /ZrO ₂	151	95.3
30-MoO ₃ /ZrO ₂	105	89.9

Table 2. Acid Strengths of Some Samples

Hammett indicator	pKa	ZrO ₂	5-MoO ₃ /ZrO ₂ (500)
Benzeneazodiphenylamine	+1.5	+	+
Dicinnamalacetone	-3.0	-	+
Benzalacetophenone	-5.6	-	+
Anthraquinone	-8.2	-	+
Nitrobenzene	-12.4	-	+
2,4-dinitrofluorobenzene	-14.5	-	+

and ZrO₂ delays the transition of ZrO₂ from amorphous to anatase phase.²⁶ Consequently, the exothermic peaks appear at 484 °C for 1-MoO₃/ZrO₂, 500 °C for 5-MoO₃/ZrO₂, and 516 °C for 10-MoO₃/ZrO₂. These results are in good agreement with those of XRD described above.

Surface Properties. It is necessary to examine the effect of molybdenum oxide on the surface properties of catalysts, that is, specific surface area, acidity, and acid strength. The specific surface areas of samples calcined at 500 °C for 3 hr are listed in Table 1. The presence of molybdenum oxide strongly influences the surface area in comparison with the pure ZrO₂. Specific surface areas of MoO₃/ZrO₂ samples are much larger than that of pure ZrO₂ calcined at the same temperature, showing that surface area increases gradually with increasing molybdenum oxide content up to 15 wt% of MoO₃. It seems likely that the interaction between molybdenum oxide and ZrO₂ protects catalysts from sintering.

The acid strength of the catalysts was examined by a color change method, using Hammett indicator in sulphuryl chloride.^{24,27} The results are listed in Table 2. In this table, (+) indicates that the color of the base form was changed to that of the conjugated acid form. ZrO₂ evacuated at 400 °C for 1 h has an acid strength $H_0 \leq +1.5$, while 5-MoO₃/ZrO₂ was estimated to have a $H_0 \leq -14.5$, indicating the formation of new acid sites stronger than those of single oxide components. Acids stronger than $H_0 \leq -11.93$, which corresponds to the acid strength of 100% H₂SO₄, are superacids.²² Consequently, MoO₃/ZrO₂ catalysts would be solid superacids. The superacidic property is attributed to the double bond nature of the Mo=O in the complex formed by the interaction of ZrO₂ with molybdate, in analogy with the case of ZrO₂ modified with tungstate, chromate, and sulfate ion.^{21,22,25,27}

The acidity of catalysts calcined at 500 °C, as determined by the amount of NH₃ irreversibly adsorbed at 230 °C,^{21,24} is listed in Table 1. As listed in Table 1, the acidity increases upon the addition of 1 wt% molybdenum oxide to ZrO₂, giving a maximum at 3 wt% of MoO₃, and then the acidity decreases with increasing molybdenum oxide content. Many combinations of two oxides have been reported to generate acid sites on the surface.⁴¹ The combination of ZrO₂ and MoO₃ probably generates stronger acid sites and more acidity as compared with the separate components. However, the surface area exhibited a maximum at 15 wt% of MoO₃, as listed in Table 1. That is, the maximum values in surface area and acidity appears at different MoO₃ content,

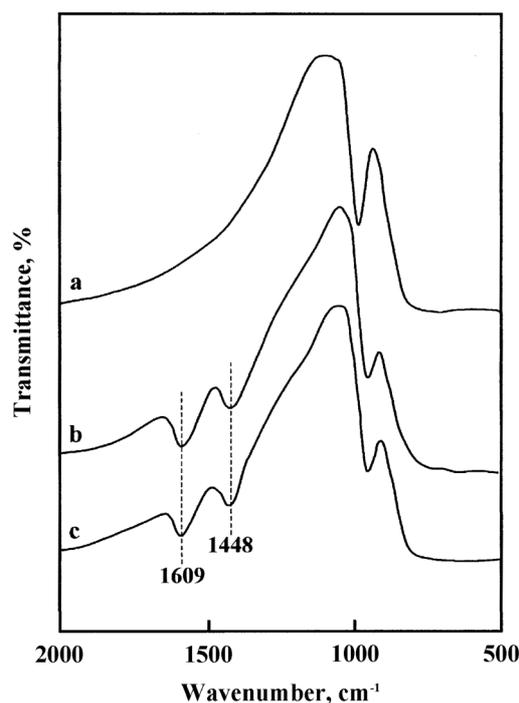


Figure 9. Infrared spectra of NH₃ adsorbed on 5-MoO₃/ZrO₂(500): (a) background of 5-MoO₃/ZrO₂(500) evacuated at 400 °C, (b) NH₃ adsorbed on 5-MoO₃/ZrO₂(500), and (c) b sample evacuated at 230 °C for 0.5 hr.

respectively. Such differences are probably due to the basicity of ammonia or due to the different extent which ammonia and N₂ diffuse into the interior of MoO₃/ZrO₂ micro-pores, respectively. In fact, it is known that the various bases are adsorbed to different extents even by the same catalyst.⁴¹

Infrared spectroscopic studies of ammonia adsorbed on

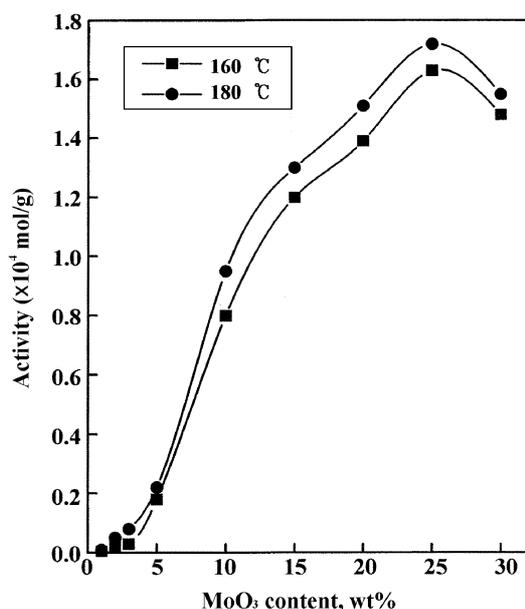


Figure 10. Catalytic activities of MoO₃/ZrO₂(500) for 2-propanol dehydration as a function of MoO₃ content.

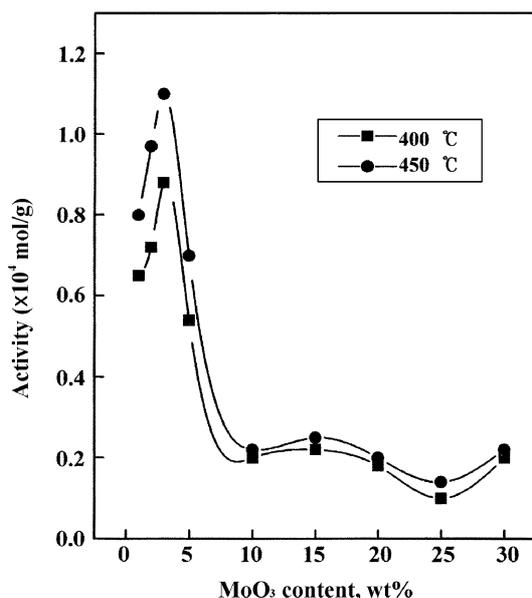


Figure 11. Catalytic activities of MoO₃/ZrO₂(500) for cumene dealkylation as a function of MoO₃ content.

solid surface have made it possible to distinguish between Brønsted and Lewis acid sites.⁴² Figure 9 shows the IR spectra of ammonia adsorbed on 5-MoO₃/ZrO₂(500) evacuated at 400 °C for 1 hr. For 5-MoO₃/ZrO₂(500), the bands at 1448 are the characteristic peaks of ammonium ion, which are formed on the Brønsted acid sites and the other set of adsorption peaks at 1609 cm⁻¹ is contributed by ammonia coordinately bonded to Lewis acid sites,⁴² indicating the presence of both Brønsted and Lewis acid sites. Other samples having different MoO₃ contents also showed the presence of both Lewis and Brønsted acid sites. Therefore, these MoO₃/ZrO₂ samples can be used as catalysts for Lewis or Brønsted acid catalysis.

Catalytic activities for acid catalysis. It is interesting to examine how the catalytic activity of acid catalyst depends on the acidic property. The catalytic activities for the 2-propanol dehydration and cumene dealkylation are measured and the results are illustrated as a function of MoO₃ content in Figures 10 and 11, respectively, where reaction temperatures are 160-180 °C for 2-propanol dehydration and 400-450 °C for cumene dealkylation. In view of Table 2 and Figures 10 and 11, the variation in catalytic activity for 2-propanol dehydration is not correlated with the change of acidity. However, the variation in catalytic activity for cumene dealkylation is roughly correlated with that of acidity. The differences of catalytic activities for both reactions against acidity are due to the difference of necessary acid strength for both reactions to occur. In fact, it has been known that 2-propanol dehydration takes place very readily on weak acid sites, while cumene dealkylation does on relatively strong acid sites.⁴³ Therefore, in the case of MoO₃/ZrO₂(500), it is concluded that the number of weak acid sites is maximum for 25-MoO₃/ZrO₂(500), while that of strong acid sites is maximum for 3-MoO₃/ZrO₂(500). In view of the catalytic data shown in Figures 10 and 11 for 2-propanol dehydration

and cumene dealkylation reactions, where the reaction temperature were 160-180 °C for the former and 400-450 °C for the latter, it is clear that 2-propanol dehydration takes place more readily than cumene dealkylation.

Conclusions

This paper has shown that a combination of FTIR, Raman spectroscopy, DSC, and XRD can be used to perform the characterization of MoO₃/ZrO₂ prepared by modifying ZrO₂ with MoO₃ and calcining in air. The interaction between molybdenum oxide and zirconia influences the physico-chemical properties of prepared catalysts with calcination temperature. The specific surface area of MoO₃/ZrO₂(500) increased in proportion to the molybdenum oxide content up to 15 wt%. Since the ZrO₂ stabilizes the surface molybdenum oxide species, for the samples equal to or less than 30 wt%, molybdenum oxide was well dispersed on the surface of zirconia, showing no phase of crystalline MoO₃ at any calcination temperature. Upon the addition of only a small amount of molybdenum oxide (1 wt%) to zirconia, both the acidity and acid strength of the catalyst increases remarkably, showing the presence of Brønsted and Lewis acid sites on the surface of MoO₃/ZrO₂. The high acid strength and high acidity are responsible for the Mo=O bond nature of complex formed by the interaction between MoO₃ and ZrO₂. The catalytic activities of MoO₃/ZrO₂ catalysts for cumene dealkylation were roughly correlated with their acidity, while those for 2-propanol dehydration which takes place readily on weak acid sites were not correlated with the acidity.

Acknowledgements. This research was supported by Kyungpook National University Research Team Fund, 2002 and was partially supported by grant No. (R05-2003-000-10074-0) from the Basic Research Program of the Korea Science and Engineering Foundation. We wish to thank Korea Basic Science Institute (Daegu Branch) for the use of X-ray diffractometer and Raman spectrometer.

References

- Martin, C.; Martin, I.; Rives, V. *J. Chem. Soc. Faraday Trans.* **1993**, *89*, 4131.
- Niwa, M.; Yamada, H.; Murakami, Y. *J. Catal.* **1992**, *134*, 331.
- Matsuoka, Y.; Niwa, M.; Murakami, Y. *J. Phys. Chem.* **1990**, *94*, 1477.
- Miyata, H.; Tokuda, S.; Ono, T.; Ohno, T.; Hatayama, F. *J. Chem. Soc., Faraday Trans.* **1990**, *86*, 2291.
- Miyata, H.; Tokuda, S.; Ono, T.; Ohno, T.; Hatayama, F. *J. Chem. Soc., Faraday Trans.* **1990**, *86*, 3659.
- Afanasyev, P.; Geantet, C.; Breyse, M. *J. Catal.* **1995**, *153*, 17.
- Okamoto, Y.; Imanaka, T.; Teramishi, S. *J. Phys. Chem.* **1981**, *85*, 3798.
- Ono, T.; Anpo, M.; Kabokawa, Y. *J. Phys. Chem.* **1986**, *90*, 4780.
- Quincy, R. B.; Houalla, M.; Proctor, A.; Hercules, D. M. *J. Phys. Chem.* **1990**, *94*, 1520.
- Zhao, B.; Wang, X.; Ma, H.; Tang, Y. *J. Mol. Catal. A: Chemical* **1996**, *108*, 167.
- Ng, K. Y. S.; Guilari, E. *J. Catal.* **1985**, *92*, 340.

12. Jin, Y. S.; Auroux, A.; Védrine, J. C. *J. Chem. Soc. Faraday Trans.* **1989**, 83, 4179.
 13. Maity, S. K.; Rana, M. S.; Srinivas, B. N.; Bej, S. K.; Murali. Dhar, G.; Prasada Rao, T. S. R. *J. Mol. Catal. A: Chemical* **2000**, 153, 121.
 14. Brown, A. S. C.; Hargreaves, J. S. J.; Taylor, S. H. *Catal. Lett.* **1999**, 57, 109.
 15. Chen, K.; Xie, S.; Tglesia, E.; Bell, A. T. *J. Catal.* **2000**, 189, 421.
 16. Ebitani, K.; Konish, J.; Hattori, H. *J. Catal.* **1991**, 130, 257.
 17. Vaudagna, S. R.; Conelli, R. A.; Canavese, S. A.; Figoli, N. S. *J. Catal.* **1997**, 169, 389.
 18. Arata, K. *Adv. Catal.* **1990**, 37, 165.
 19. Imamura, S.; Sasaki, H.; Shono, M.; Kanai, H. *J. Catal.* **1998**, 177, 72.
 20. Desikan, A. N.; Huang, L.; Oyama, S. T. *J. Phys. Chem.* **1991**, 95, 10050.
 21. Sohn, J. R. *J. Ind. Eng. Chem.* **2004**, 10, in press.
 22. Sohn, J. R.; Kwon, T. D.; Kim, S. B. *J. Ind. Eng. Chem.* **2001**, 7, 441.
 23. Sohn, J. R.; Seo, K. C.; Pae, Y. I. *Bull. Korean Chem. Soc.* **2003**, 24, 311.
 24. Sohn, J. R.; Cho, S. G.; Pae, Y. I.; Hayashi, S. *J. Catal.* **1996**, 159, 170.
 25. Sohn, J. R.; Park, M. Y. *Langmuir* **1998**, 14, 6140.
 26. Sohn, J. R.; Ozaki, A. *J. Catal.* **1980**, 61, 29.
 27. Sohn, J. R.; Ryu, S. G. *Langmuir* **1993**, 9, 126.
 28. Smith, M. R.; Ozkan, U. S. *J. Catal.* **1993**, 141, 124.
 29. Liu, Z.; Chen, Y. *J. Catal.* **1998**, 177, 314.
 30. Mestl, G.; Srinivasan, T. K. *Cat. Rev. Sci. Eng.* **1998**, 40, 451.
 31. Dufresne, P.; Payen, E.; Grimblot, J.; Bonnelle, J. P. *J. Phys. Chem.* **1981**, 85, 2344.
 32. Hu, H.; Wachs, I. E. *J. Phys. Chem.* **1995**, 99, 10897.
 33. Roark, R. D.; Kohler, S. D.; Ekerdt, J. G.; Kim, D. S.; Wachs, I. E. *Catal. Lett.* **1992**, 16, 77.
 34. Schild, C. H.; Wokaun, A.; Köppel, R. A.; Baiker, A. *J. Catal.* **1991**, 130, 657.
 35. Sohn, J. R.; Doh, I. J.; Pae, Y. I. *Langmuir* **2002**, 18, 6280.
 36. Scheithauer, M.; Grasselli, R. K.; Knözinger, H. *Langmuir* **1998**, 14, 3019.
 37. Litteti, L.; Nova, I.; Ramis, G.; Dall'Acqua, L.; Busca, G.; Giamello, E.; Forzatti, P.; Bregani, F. *J. Catal.* **1999**, 187, 419.
 38. Kim, D. S.; Ostromecki, M.; Wachs, I. E. *J. Mol. Catal. A: Chemical* **1996**, 106, 93.
 39. Larsen, G.; Lotero, E.; Petkovic, L. M.; Shobe, D. S. *J. Catal.* **1997**, 169, 67.
 40. Afanasiev, P.; Geantet, C.; Breyse, M.; Coudurier, G.; Védrine, J. C. *J. Chem. Soc., Faraday Trans., 1* **1994**, 190, 193.
 41. Tanabe, K.; Misono, M.; Ono, Y.; Hattori, J. *New Solid Acids and Bases*; Elsevier Science: Amsterdam, 1989; p 108.
 42. Satsuma, A.; Hattori, A.; Mizutani, K.; Furuta, A.; Niyamoto, A.; Hattori, T.; Murakami, Y. *J. Phys. Chem.* **1988**, 92, 6052.
 43. DeCanio, S. J.; Sohn, J. R.; Fritz, P. O.; Lunsford, J. H. *J. Catal.* **1986**, 101, 132.
-