

Interactive CO₂ Adsorption on the BaO (100) Surface: A Density Functional Theory (DFT) Study

Soonchul Kwon,^{†,‡} JungBae Hwang,^{‡,§} Hanlim Lee,[#] and Wang Ro Lee^{P,*}

[†]School of Civil and Environmental Engineering, Georgia Institute of Technology, Atlanta, GA 30332, U.S.A.

[‡]Spectro, 261-Cheomdan-gwagi-ro, Buk-gu, Gwangju 500-712, Korea

[§]School of Electronics and Computer Engineering, Chonnam National University, Gwangju 500-757, Korea

[#]Department of Atmospheric Sciences, Yonsei University, Seoul 120-749, Korea

^PFaculty of Liberal Education, Chonbuk National University, Jeonju, Jeonbuk 561-756, Korea

*E-mail: wrlee@jbnu.ac.kr

Received May 28, 2010, Accepted June 15, 2010

A density functional theory (DFT) study of CO₂ adsorption on barium oxide (BaO) adsorbents is conducted to understand the chemical activity of the oxygen site on the BaO (100) surface. This study evaluated the adsorption energies and geometries of a single CO₂ molecule and a pair of CO₂ molecules on the BaO (100) surface. A quantum calculation was performed to obtain information on the molecular structures and molecular reaction mechanisms; the results of the calculation indicated that CO₂ was adsorbed on BaO to form a stable surface carbonate with strong chemisorption. To study the interactive CO₂ adsorption on the BaO (100) surface, a pair of CO₂ molecules was bound to neighboring and distant oxygen sites. The interactive CO₂ adsorption on the BaO surface was found to slightly weaken the adsorption energy, owing to the interaction between CO₂ molecules.

Key Words: Density functional theory, Adsorption, BaO, CO₂

Introduction

Carbon dioxide is a major contributor to the greenhouse effect. Over 80% of CO₂ emissions by human beings are a result of energy production.¹ Therefore, reducing CO₂ emissions from energy sources is absolutely necessary to mitigate climate change. Among the numerous sources of CO₂ emissions, power plants are the largest point source, comprising approximately 41% of the total emissions; therefore, CO₂ must be separated from the released flue gas mixture.² For highly efficient CO₂ separation processes, CO₂ adsorption on a solid sorbent can be a method with a good potential because of its low operating costs and low energy demands.³⁻⁶ Among various adsorption methods that use different adsorbents, mineral carbonation has the potential for CO₂ separation because it leads to the formation of stable carbonates, minimizing the leakage of CO₂ into the atmosphere after capture. Because mineral carbonation is the reaction between CO₂ and metal oxides to form carbonates, quantum chemical calculations can be performed to evaluate the adsorption mechanism of CO₂ on the surface of a solid sorbent.

This study investigates CO₂ adsorption on barium oxide (BaO) because the BaO surface provides a simple cubic structure as well as a simple surface product layer (BaCO₃).⁷ In addition, the BaO surface has a high reactivity that enables it to donate charge to the adsorbed CO₂ molecule; the high reactivity can be attributed to the fact that it has a high basicity resulting from the low Madelung potential energy.⁸ The quantum chemical calculation of CO₂ adsorption on BaO has been already studied,^{7,9-12} but the previous studies did not examine the interactive adsorption of CO₂ molecules on O sites on the BaO surface; this study investigates the interaction effect of CO₂ molecules.

To explore CO₂ molecular adsorption, a density functional

theory (DFT) study is performed to evaluate the adsorption properties of CO₂ on surface materials. DFT calculation was chosen as it yields high accuracy for adsorption energy and geometry.^{11,13} To determine adsorption properties, this study examines the adsorption geometry and the adsorption energy of CO₂ on BaO (100) using a periodic-slab calculation. For the minimized geometry configuration, the adsorption energy of surface coverage is discussed. The structure optimization and energy information enable us to determine the basis of the reaction mechanism of CO₂ adsorption on the BaO surface.

Calculation Details

This study utilized DFT calculations to evaluate the CO₂ adsorption on O sites on the BaO surface in the periodic slab model. Geometry optimizations were performed using Dmol³ under the following conditions: (i) The general gradient approximation (GGA) was at the PBE level for functional option and (ii) the DND basis to predict the properties of adsorbents and adsorbates was employed because PBE shows good performance for relevant adsorbates and DND provides a good agreement with the experimental data.^{9,14-16}

For the quantum calculation, three-dimensional periodic slab models were employed.^{7,12} In the supercell, the sorbent surface was exposed as a slab, providing three layers. For the development of the surface structure, three atomic layers were cleaved at the (100) plane. Vacuum thickness (size of unit cell perpendicular to slab-slab thickness) was set to 10 Å. All three layers were geometry-optimized without constraint.

Coverage study determines the minimized adsorption energy between adsorbate molecules and adsorbents. It also evaluates the effect of the self-interaction of CO₂ molecules in the super-

cell. Adsorption coverage θ as a function of the different lattice size of the supercell is prepared from the coverage ($\theta = 0.5, 0.125, 0.056, \text{ and } 0.032$) of an adsorbed CO_2 molecule on the center atom of a (1×1) , (2×2) , (3×3) , and (4×4) unit cell, respectively. For the interactive adsorption, a pair of CO_2 molecules was bound to both neighboring sites and distant sites on the BaO (100) surface.

To determine adsorption energies E_{ads} between the adsorbate and the adsorbent surface, three single total energy calculations are used for: (i) geometry optimization of the adsorbate, (ii) geometry optimization of the adsorbent surface slab without the adsorbate, and (iii) geometry optimization of the adsorbent surface slab with the adsorbate. The adsorption energies were determined in the following way:

$$E_{ads} = E_{(adsorbent+adsorbate)} - (E_{adsorbent} + E_{adsorbate}) \quad (1)$$

where E_{ads} is the adsorption energy of the adsorbate on the adsorbent, $E_{(adsorbent+adsorbate)}$ the total energy of the adsorbate with the adsorbent, $E_{adsorbent}$ the total energy of the adsorbent, and $E_{adsorbate}$ the total energy of the adsorbate. Using the calculation of adsorption energy, the adsorption properties of adsorbates on BaO are discussed.

Results and Discussion

Geometry optimization of bulk adsorbent and CO_2 molecules. After the geometry optimization of the 1×1 BaO (100) surface (unit cell), the surface was not relaxed, as shown in Table 1. After the interaction of CO_2 with 1×1 BaO (100), the surface relaxation of both O and Ba sites was observed. The O site where CO_2 was bonded was considerably relaxed and the Ba site surrounding the O- CO_2 site was also symmetrically relaxed compared to the origin of the BaO surface. Table 2 presents the geometry properties of bulk BaO and CO_2 molecules. The calculated bond length and bond angles are in a good agreement (within 1.7%) with the experimental data and another DFT calculation.^{11,17,18}

CO_2 adsorption on BaO. Figure 1 shows the optimized geometries for the CO_2 adsorption on the 2×2 BaO (100) surface,

forming a single carbonate layer (BaCO_3). During the interaction between BaO and CO_2 , a charge rearrangement results in the linking between the CO_2 molecule and the O site. The charged site on the surface provided the strong bond (bond length = 1.389 Å) of $\text{O}_{\text{surface}}\text{-CO}_2$ because the adsorbed CO_2 at the charged O site formed charged molecules, resulting from charge transfers from the BaO surface to CO_2 ; this weakened the O-C bond for CO_2 and the CO_2 molecule bended. The electrostatic stabilization of the CO_2 molecule on the BaO surface relied on the affinity of CO_2 to the O site for the high interaction with the charge distribution in the lattice. The larger lattice parameter provides the smaller internal Madelung stabilization, leading to the larger charge transfer.¹⁰ Because the cubic lattice parameter of BaO (5.5 Å) is larger than that of MgO (4.21 Å) reported by experiment, the charge transfer from the BaO surface is larger than that from MgO, evidencing the relatively strong interaction of CO_2 with BaO compared to other metal oxides.¹⁹ Therefore, the DFT calculation can support the strong formation of a surface carbonate.

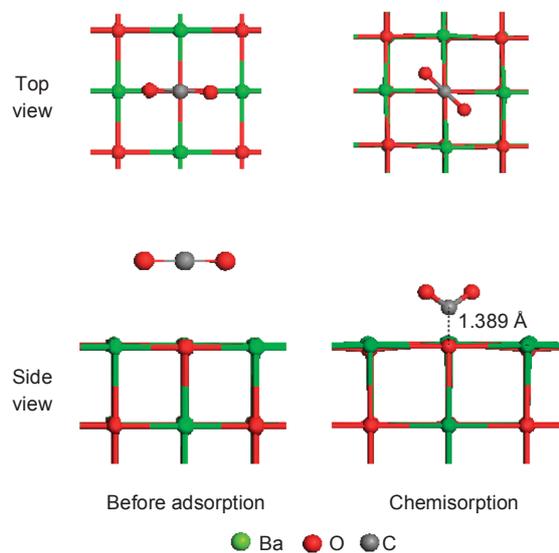


Figure 1. Geometries before/after CO_2 adsorption on the 2×2 BaO (100) surface.

Table 1. Geometry optimization of the 1×1 BaO (100) surface and CO_2 adsorption on the 1×1 BaO (100) surface

	BaO (100)		BaO (100)- CO_2			
	Bond length of $\text{O}_{\text{surface}}$ (Å)	Bond length of $\text{Ba}_{\text{surface}}$ (Å)	Bond length of $\text{O}_{\text{surface}}$ (Å)	Bond length of $\text{O}_{\text{surface}}\text{-CO}_2$ (Å)	Bond length of $\text{Ba}_{\text{surface},1}$ (Å) ^a	Bond length of $\text{Ba}_{\text{surface},2}$ (Å) ^b
1st to 2nd atomic layer	2.961	3.005	2.742	3.067	3.013	3.031
2nd to 3rd atomic layer	2.961	3.005	2.966	2.813	3.095	3.088

^aUp and down Ba site located near the $\text{O}_{\text{surface}}$ site of BaO bound to CO_2 . ^bLeft and right Ba site located near the $\text{O}_{\text{surface}}$ site of BaO bound to CO_2 .

Table 2. Geometry properties of bulk BaO and CO_2 molecules obtained by DFT calculation

	This study		Tutuianu <i>et al.</i> ¹¹		Experiment ^{17,18}	
	Bond length (Å)	Bond angle (°)	Bond length (Å)	Bond angle (°)	Bond length (Å)	Bond angle (°)
BaO (cubic bulk)	2.76		2.78		2.76	
CO_2	1.18	179.9	1.17	179.9	1.16	180

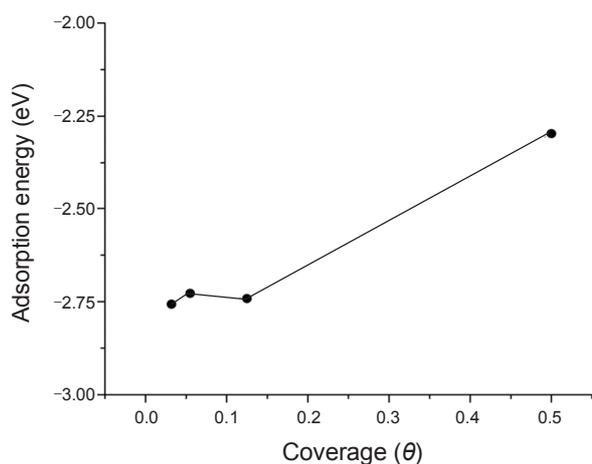


Figure 2. Effect of CO₂ adsorption energy as a function of coverage (θ).

For the evaluation of the lowest energy minimized (100) structures for adsorption, Figure 2 represents the CO₂ chemisorption with respect to coverage. The adsorption energy is described as a function of coverage ($\theta = 0.032, 0.055, 0.125$, and 0.5), resulting in the strong dependence of adsorption properties on coverage. As coverage decreases, the adsorption energy decreases, indicating that the chemisorbed CO₂ becomes significantly stable. The adsorption energy (-2.30 eV) at coverage $\theta = 0.5$ (in a (1×1) supercell) is higher than that at other coverages due to the self-interaction of the CO₂ molecule in a small cell ($5.52 \text{ \AA} \times 5.52 \text{ \AA}$). Table 3 presents the adsorption properties of CO₂ on the BaO (100) surface, dependent on coverage. The bond length of O_{surface}-C at $\theta = 0.5$ is 1.414 \AA while that at $\theta = 0.125$ is 1.389 \AA . This result supports the effect of self-interaction of CO₂ molecules, resulting in a relatively weaker chemisorption. At less than 0.125 of coverage, the energy of adsorption is minimized, leading to the optimized geometry of CO₂ adsorption on the BaO (100) surface in a supercell greater than a (2×2) supercell. The adsorption energy of CO₂ is thus -2.74 eV, according to DFT calculation. This low value indi-

cates that CO₂ adsorption is energetically more favorable to the BaO surface than CaO (-1.0 eV) and MgO (-1.2 eV).^{20,21}

Compared to the DFT study by another group (bond length (O-C) = 1.23 \AA , bond angle (OCO) = 131.6°), this study (bond length (O-C) = 1.27 \AA , bond angle (OCO) = 128.1°) showed better agreement with the experimental data (bond length (O-C) = 1.30 \AA , bond angle (OCO) = 120°) because they did not consider the self-interaction of CO₂ in the small size of the periodic cell.^{11,18} The adsorption energy obtained in our study is in poor agreement with their results because a different tool and different calculation conditions were employed. Their adsorption energy (-0.8 eV) at $\theta = 0.5$ is higher than the CO₂ adsorption energy (-1.0 eV) on the CaO surface (as reported by the Paccioni group).^{11,20} This indicates that the interaction of BaO to CO₂ is smaller than that of CaO, but does not explain the correlation between surface activity and basicity because the base strength of BaO is higher than CaO, leading to the higher affinity of CO₂ adsorption.^{8,20}

Interactive CO₂ adsorption on BaO. Because many CO₂ molecules can be adsorbed on the O sites of metal oxides, and the DFT calculation of interactive (bound to neighboring sites and distant sites) CO₂ adsorption on the BaO surface has not yet been studied, we investigate the geometry and energy of the interactive CO₂ adsorption. Interaction energy was calculated as follows:

$$E_{Int} = 2 \times E_{ads,1CO_2} - E_{ads,2CO_2} \quad (2)$$

where E_{Int} denotes the interaction energy of a pair of CO₂ molecules (eV); $E_{ads,1CO_2}$, a single CO₂ adsorption energy molecule (eV); and $E_{ads,2CO_2}$, a pair of CO₂ adsorption molecules (eV). A pair of CO₂ adsorption molecules on the surface is slightly less favorable than molecular CO₂ adsorption on both neighboring and distant surface sites, as illustrated in Figure 3 and Table 4. Compared to the energy of the purely isolated molecular adsorption of CO₂ ($2 \times E_{ads,1CO_2}$), the energy of interactive adsorption is slightly higher, indicating the slightly less stable formation of carbonate due to the interaction of CO₂ molecules on the

Table 3. Adsorption properties of single molecular CO₂ on the BaO (100) surface

Coverage (θ)	Bond length (O _{surface} -CO ₂) (Å)	Bond length (O-C, CO ₂) (Å)	Bond angle ($^\circ$)	Adsorption energy (eV)	Adsorption energy of reference (eV) ¹¹
Experiment ¹⁸		1.30	120		
0.5	1.414	1.269	128.1	-2.30	-0.8
0.125	1.389	1.278	126.7	-2.74	-1.7
0.055	1.387	1.278	126.4	-2.73	
0.032	1.386	1.277	126.3	-2.76	

Table 4. Adsorption properties of a pair of CO₂ molecules on the 2×2 BaO (100) surface

	Adsorption energy (eV)	Bond length (CO ₂ -CO ₂) (Å)	Bond length (O _{surface} -CO ₂) (Å)	Interaction energy of CO ₂ -CO ₂ (eV)
Single	-2.742		1.389	
Distant sites	-5.326	7.811	1.393	-0.158
Neighboring sites	-5.321	3.771	1.389	-0.163

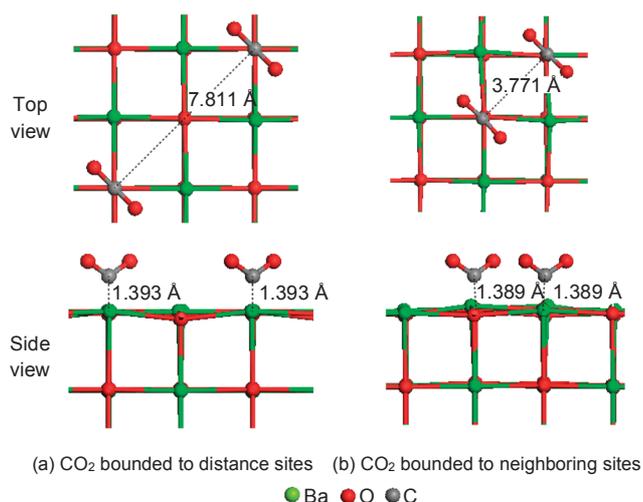


Figure 3. Geometries of CO₂ adsorbed to distant (a) and neighboring sites (b) on the 2 × 2 BaO (100) surface.

surface. Because CO₂ molecules are close, their interaction on the surface increases slightly. However, the bond length of O_{surface}-CO₂ does not significantly depend on the interaction of CO₂ although CO₂ molecules are close. An analysis of surface interaction energies can ensure the energetic feasibility of a number of CO₂ adsorption molecules on the adsorbent surface.

In conclusion, the quantum chemical study by DFT calculation using Dmol³ represents geometric parameters and adsorption energies of CO₂ on the BaO (100) surface. A pair of CO₂ interaction molecules on the BaO surface is investigated to evaluate the interaction effect between CO₂ molecules for the surface adsorption. This result indicates that CO₂ interaction weakens the adsorption energy. This DFT study can predict the adsorption properties of CO₂ on the BaO surface and can identify the basic quantum adsorption mechanism of the BaO carbonation for CO₂ capture.

Acknowledgments. This subject is supported by Ministry of Environment as "The Eco-technopia 21 project" in Korea.

References

1. Environmental Protection Agency 2008.
2. International Energy Agency 2009.
3. Meisen, A.; Shuai, X. S. *Energy Conversion and Management* **1997**, *38*, S37.
4. Khatri, R. A.; Chuang, S. S. C.; Soong, Y.; Gray, M. *Industrial & Engineering Chemistry Research* **2005**, *44*, 3702.
5. Khatri, R. A.; Chuang, S. S. C.; Soong, Y.; Gray, M. *Energy & Fuels* **2006**, *20*, 1514.
6. Plaza, M. G.; Pevida, C.; Arenillas, A.; Rubiera, F.; Pis, J. J. *Fuel* **2007**, *86*, 2204.
7. Broqvist, P.; Panas, I.; Gronbeck, H. *Journal of Physical Chemistry B* **2005**, *109*, 15410.
8. Freund, H. J.; Roberts, M. W. *Surface Science Reports* **1996**, *25*, 225.
9. Broqvist, P.; Gronbeck, H.; Fridell, E.; Panas, I. *Journal of Physical Chemistry B* **2004**, *108*, 3523.
10. Karlsten, E. J.; Nygren, M. A.; Pettersson, L. G. M. *Journal of Physical Chemistry B* **2003**, *107*, 7795.
11. Tutuianu, M.; Inderwildi, O. R.; Bessler, W. G.; Warnatz, J. *Journal of Physical Chemistry B* **2006**, *110*, 17484.
12. Broqvist, P.; Panas, I.; Fridell, E.; Persson, H. *Journal of Physical Chemistry B* **2002**, *106*, 137.
13. Gronbeck, H. *Journal of Physical Chemistry B* **2006**, *110*, 11977.
14. Perdew, J. P.; Burke, K.; Ernzerhof, M. *Chemical Applications of Density-Functional Theory* **1996**, *629*, 453.
15. Accelrys, Inc. 2005 Dmol³, San Diego.
16. Perdew, J. P.; Burke, K.; Ernzerhof, M. *Physical Review Letters* **1996**, *77*, 3865.
17. Galasso, F. S. *Structure and Properties of Inorganic Solids*; Pergamon Press: 1970; Oxford.
18. Holleman, A. F.; Wiberg, E. *Lehrbuch der Anorganischen Chemie*; Walter de Gruyter: Berlin, 1995; New York.
19. Wyckoff, R. W. G. *Crystal Structure*; Interscience Publishers (John Wiley): 1965; New York.
20. Pacchioni, G.; Ricart, J. M.; Illas, F. *Journal of the American Chemical Society* **1994**, *116*, 10152.
21. Yanagisawa, Y.; Takaoka, K.; Yamabe, S. *Journal of the Chemical Society-Faraday Transactions* **1994**, *90*, 2561.