


Scheme 2. Molecular structure of the donor and acceptors used in this work.

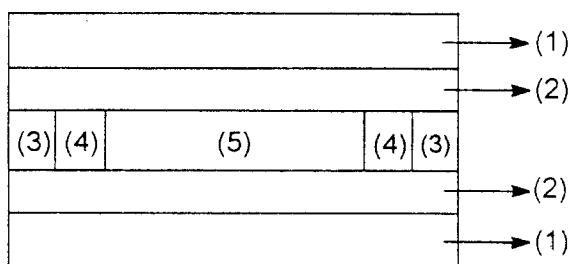

Scheme 3. ECD cell construction. (1) Slide glass, (2) ITO film, (3) Epoxy resin, (4) PET spacer, (5) Sample

used to find the stoichiometry of the complex formation. The total concentration of the mixture was fixed at 0.05 M (3-4a) and 0.025 M (3-4b) while the relative concentrations of donor and acceptor were varied. The maximum absorbance was observed for the 1:1 molar mixture, indicating one donor molecule forms the complex with an acceptor molecule, *i.e.*, a 1:1 complex was formed.

Preparation of the Electrochromic Display (ECD) Cell. The ECD cell, consisted of two glass sheets (2 cm \times 2 cm), was separated by a 0.1 mm spacer of polyester film. The glass sheets were coated on one side with transparent conductive electrodes of indium-tin oxide (ITO) and these sides were placed so as to face each other on the inside of the cell and sealed with an insulating epoxide resin (Scheme 3).

Prior to the final sealing, the space between the electrodes was filled with a dichloromethane solution containing 0.196 mM phenothiazine (3) and the same concentration of either 2,3-dichloro-1,4-naphthoquinone (4a) or 2,3-dichloro-5-nitro-1,4-naphthoquinone (4b) and 1.5 mM of tetrabutylammonium perchlorate as electrolyte.

Electrochromism Measurements. The electrodes of ECD cell were connected to a D.C-power supply (LG Co, Seoul). The ECD cell was fixed at UV/vis spectrophotometer and absorption was measured while various voltages were applied.

Results and Discussion

Intermolecular Charge Transfer Complex and Absorption Spectra. The absorption band in the visible region of intramolecular charge transfer complex was originated from the electronic transition between highest occupied molecular orbital (HOMO) and lowest unoccupied molecular orbital (LUMO) of itself.¹³ In contrast, an electron transfer between the molecules is the reason for the absorption (usually in the visible region) in the intermolecular charge transfer complex. In this study we used the molecule (3) as a donor and (4a) or (4b) as an acceptor (Scheme 2). The reason to choose these sets of the donor-acceptor is that these molecules are known to form a well-behaving charge transfer complex.¹⁴ Furthermore, the molecule (3), (4a) and (4b) does not exhibit any color when are not formed the complex, thus enable us to observe the change in the color clearly (see below).

The absorption spectrum of (3), (4a), (4b) and a charge complex formed between them is compared in Figure 1. The donor (3) and acceptor (4a) do not show an absorption band in the visible region, but the charge transfer complex

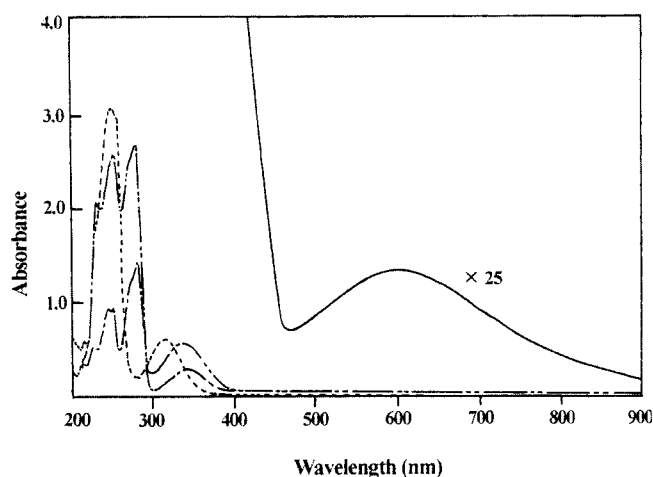


Figure 1. Absorption spectrum of donor (3) (----), acceptor (4a) (—), (4b) (····) and the 1:1 mixture of (3) and (4a) (— · —). The optical path length was 10 mm.

showed a broad absorption band in the visible region centered about 605 nm, resulting in green color. When a charge transfer was formed between donor (3) and acceptor (4b), a broad absorption band (centered about 700 nm) was apparent and the solution showed a deep-green color (Figure 2). Compared with the complex formed between (3) and (4a), the maximum of the absorption band of the complex formed between (3) and (4b) was red-shifted about 100 nm and somewhat broadened. As it is shown in the above observations, intermolecular charge transfer complex can exhibit various absorption bands, implying a possibility of use of these molecules as pigments and dyes. However, it is worthy of noting that we were not able to obtain any precipitation of above charge transfer complex in spite of their beautiful color.

Stoichiometry of the Complex Formation. The stoichiometry of the complex formation was checked by continuous variation method. The intensities of the absorption band at 605 nm (for the donor (3) and (4a) combination) and 700 nm (for donor (3) and (4b) set) were followed for the mixture with various molar ratio of the respective set of the donor and acceptor, while the total concentrations were

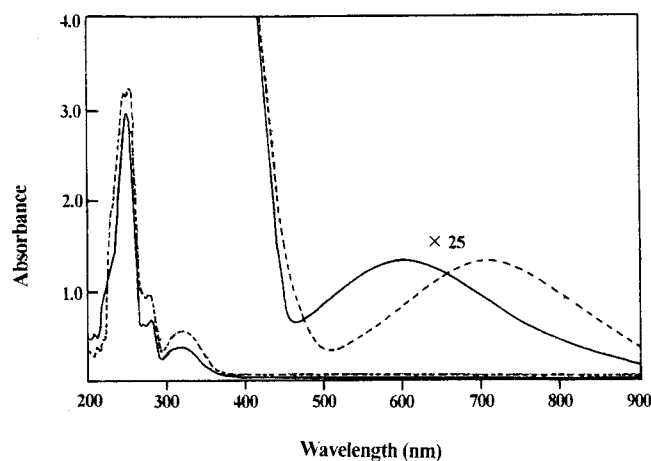


Figure 2. Absorption spectrum of the (3)-(4a) (—) and (3)-(4b) complex (----). The optical path length was 10 mm.

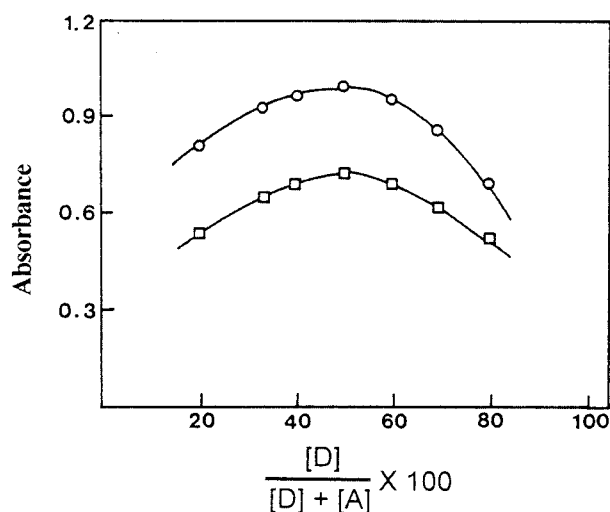


Figure 3. Variation of absorbance with molar percentage of donors. [D] and [A] denote the concentrations of the donor and acceptor. The circles represent the (3)-(4a) mixture and the squares the (3)-(4b) mixture. The total concentration of the former mixture was 0.05 M and latter 0.025 M.

kept constant (0.05 M for the (3) and (4a) set, and 0.025 M for the (3) and (4b) set). The resulting absorbance changes are depicted in Figure 3. Clear maxima in the variation method indicate that a 1 : 1 complex was formed in both cases.

Electrochromic Properties. The electrochromic properties of acceptor (4a) was probed by absorption spectrum (Figure 4). A new absorption band was appeared at 480 nm as voltage of the system is increased to 3.2 volt. This observation led us to propose reduction of (4a). The color of the transparent electrochromic (EC) cell was changed to pale-yellow as voltage was applied. The current change of the EC cell was recorded as the 3.2V of the electricity was applied (Figure 5). It was increased sharply to reach 1500 μ A then stabilized at 800 μ A after 5 seconds. Figures 6 and 7 show the electrochromic properties and the current change of the -NO₂ which was substituted at acceptor (4b). The electrochromism of the (4a) and (4b)

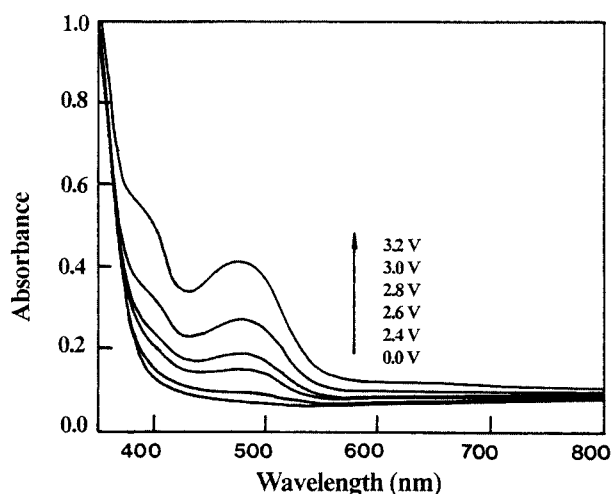


Figure 4. Absorption spectrum of 2,3 dichloro-1,4-napthoquinone, (4a), as a function of the applied electric field. The concentration was 0.196 mM and the path length was 10 mm.

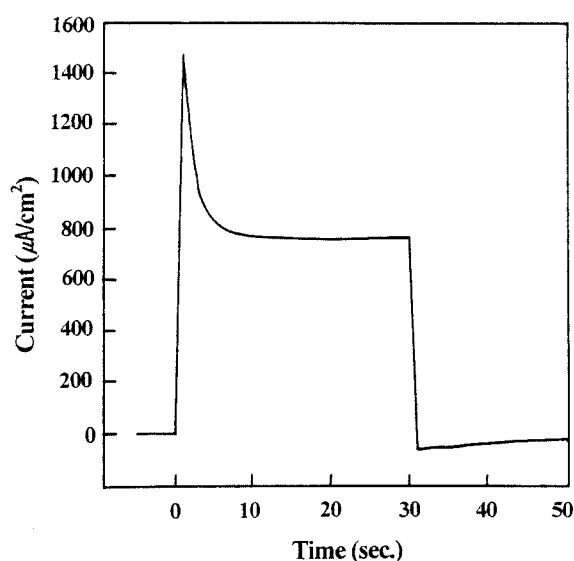


Figure 5. The change in the current with time for 2,3 dichloro-1,4-napthoquinone, (4a). The 3.2V was applied at the time 0 and turned off at 30 seconds.

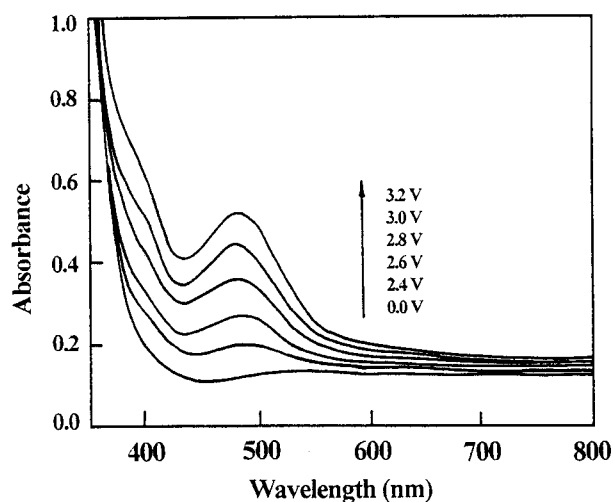


Figure 6. Absorption spectrum of 2,3 dichloro-5-nitro-1,4-napthoquinone, (4b). The conditions are the same as in Figure 4.

appeared to be similar except for the initial maximum in the current, which was 2000 μ A for (4b). Increase in the initial maximum suggests that substituted nitro group of (4b) result in stronger acceptor property compared to (4a). Electrochromism and change in the current was similarly depicted in Figures 8 and 9 for donor phenothiazine ((3), Scheme 2). The initial current reached to 276 μ A as applied voltage was 1.9V. The electrochromism and the current change for the charge transfer complex (3)-(4a) and (3)-(4b) are summarized in Figures 10 and 11, respectively. As the voltage was applied, a new absorption band of the complexes (3)-(4a), (3)-(4b) was found in the 400-500 nm region.

In a previous study Lim¹⁵ reported the appearance of similar new absorption band in the 500 nm region for polyvinyl phenothiazine film due to the electric oxidation of the film. Bodea and Silberg¹⁶ suggested that the new absorption band was the results of absorption of methyl phenothiazine radical cation.

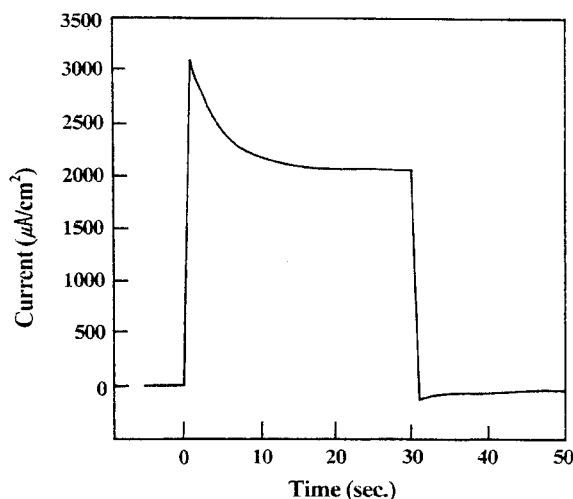


Figure 7. The change in the current with time for 2,3-dichloro-5-nitro-1,4-naphthoquinone, (4b). The 3.2 V was applied at the time 0 and turned off at 30 seconds.

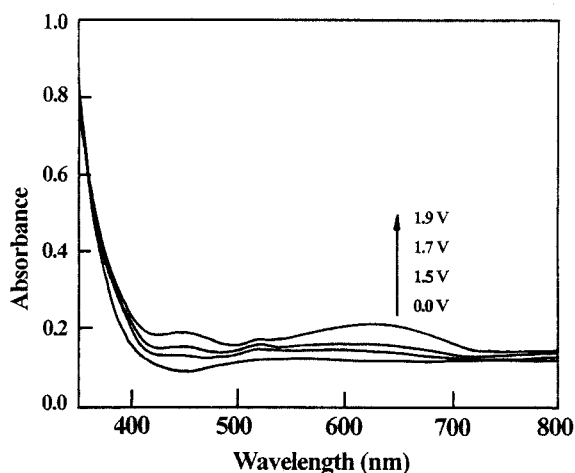


Figure 8. Absorption spectrum of phenothiazine, (3). The conditions are the same as in Figure 4, except for the applied voltage.

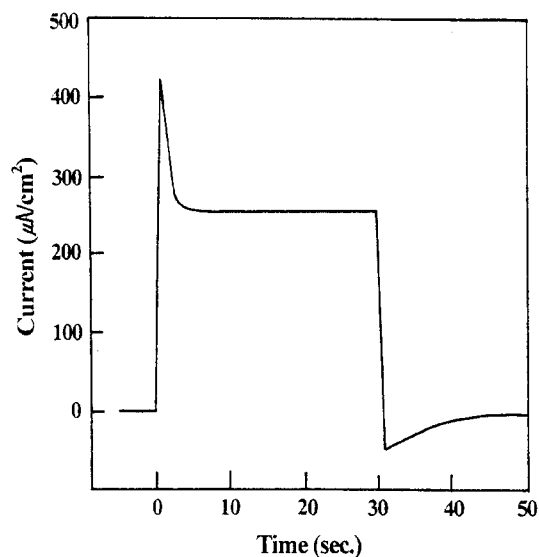


Figure 9. The change in the current with time for phenothiazine, (3). The 1.9 V was applied at the time 0 and turned off at 30 seconds.

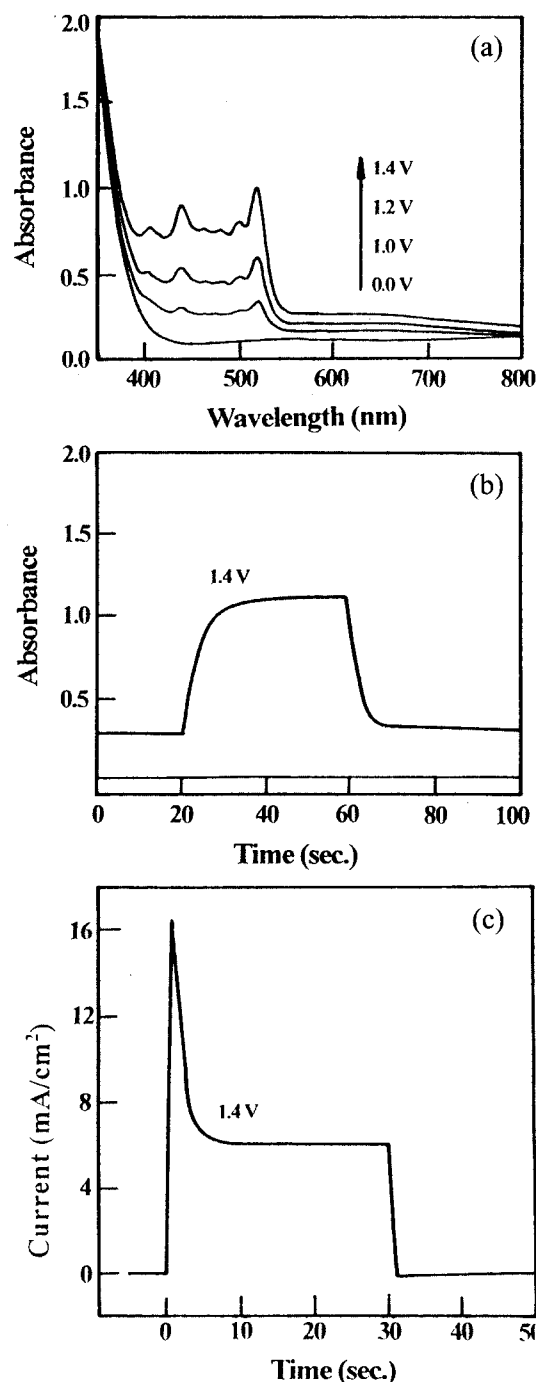


Figure 10. Effect of applied voltage in the absorption pattern (a), change in the absorbance at 510 nm (b), and the current (c). The complex was 1:1 mixture of the 0.098 mM of (3) and (4a).

Similarly, we suggest that the new absorption band appeared in 400–500 nm for both charge transfer complex is due to the formation of radical cation of phenothiazine donor. The formation of phenothiazine cation radical due to the transferring of one electron from donor (3) to one of acceptor with an applying voltage in the charge transfer complex was reported.^{1,8} As a result of applied voltage, the complexes exhibit the change in color in several ten seconds. Furthermore, these opto-electric properties were reproducible after several ten times of electricity application, indicating

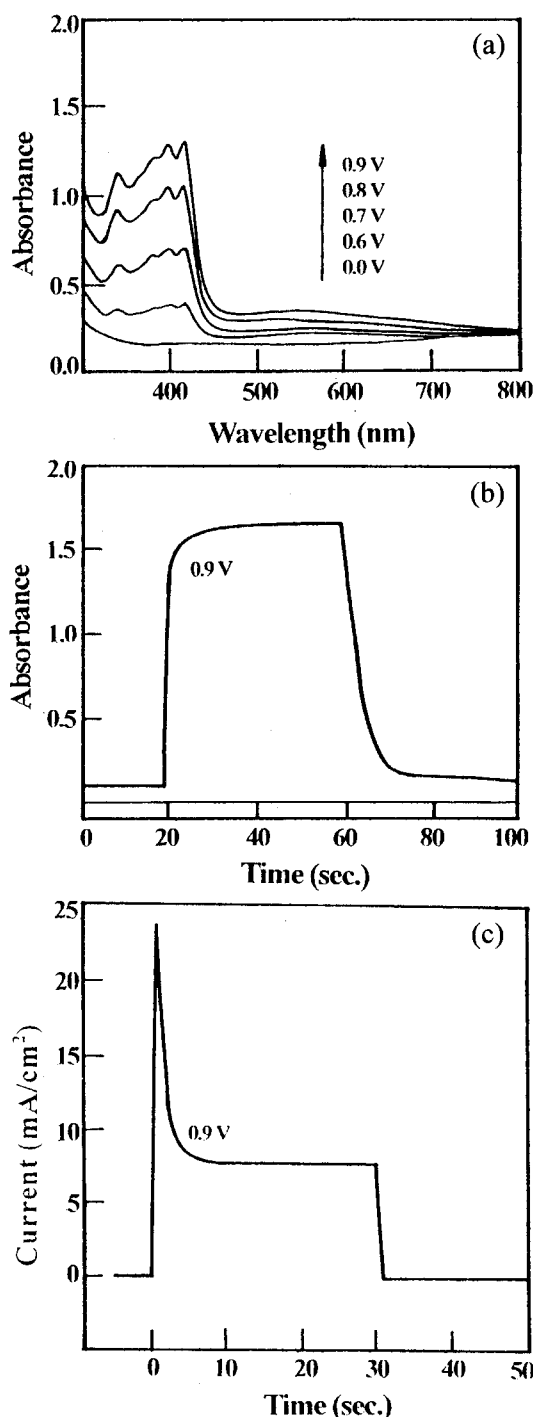


Figure 11. Effect of applied voltage in the absorption pattern (a), change in the absorbance at 510 nm (b), and the current (c). The complex was 1 : 1 mixture of the 0.098 mM of (3) and (4b).

that the complex is very stable. For the complex formed between (3) and (4a), absorption band of phenothiazine appeared at 400-500 nm with an applying voltage 1.4 volt and disappeared as the voltage was turned off. When the voltage was increased above 1.4V, the absorption band start to decreased and further increasing in the electricity results in the disappearance of the absorption band, indicating the complex was distorted. No reversibility for the complex (3)-(4a) system was observed when the voltage higher than 1.4

volt was applied.

Figure 10(b) shows the change in the absorption intensity at 510 nm with time as the 1.4V of electricity was applied. When the voltage was applied, it represented full color in 15 seconds and the absorption was reduced back to its original state in several seconds. Figure 10(c) shows that the current change with applied voltage of 0.9V for the complex (3)-(4b). After applying the voltage, surprisingly, the current reached at as high as 16 mA/cm² in 5 seconds and reached to 7 mA/cm² afterward. This value is about 10³ times higher compared to that observed from the donor (3) or acceptor (4a) and (4b). The electrochromism of (3)-(4b) (Figure 11) was basically similar to electrochromism of the complex (3)-(4a). The highest voltage of 0.9V, initial maximum of 24 mA/cm² and reversibility of 8 mA/cm² for this complex was observed. The observed 10-100 times higher current upon complex formation in the similar applied voltage indicate that a very small amount of the electricity is required for the similar color effect. This phenomenon can be ascribed to the formation of the charge transfer complex in the solution which enhances the current of the electrons compared to the solutions in which the donor or acceptor exist independently.

Conclusion

The donor and acceptor set, we synthesized here, exhibits an absorption band in the visible region by applying relatively low voltage, resulting in the rich and noble green color. When this color appears, the current of the donor-acceptor mixture was 10-100 times higher compared to donor or acceptor alone, indicating the formation of the charge transfer complex.

References

1. Nagasu, M.; Koshida, N. *Appl. Phys. Lett.* **1990**, *57*, 1324.
2. Granqvist, C. G. *Solid State Mater. Sci.* **1990**, *16*, 291.
3. Bell, J. M.; Macfarlane, D. R.; Smith, G. B.; Spiccia, L.; Watkins, I. D.; West, B. O. *Chem. Aust.* **1995**, *62*(11), 38.
4. Kawai, S. H.; Gilat, S. L.; Ponsimet, R.; Lehn, J. M. *Chem. Eur. J.* **1995**, *1*(5), 285.
5. Li, Y-M.; Kudo, T. *J. Electrochem. Soc.* **1995**, *142*, 1194.
6. Ponnese, A.; Simone, F. *Appl. Phys. A.* **1993**, *57*, 13.
7. Shiotsu, F.; Urabe, K.; Fujinami, T.; Kitao, M. *Shizuoka Daigaku Denshi Kogaku Kenkyusho Kenkyu Hokoku* **1995**, *30*, 37.
8. Zhang, X. M.; Shan, B. Z.; Bai, Z. P.; You, X. Z.; Duan, C. Y. *Chem. Mater.* **1997**, *9*, 2687.
9. Andre, J. J.; Biecker, A.; Gautier, F. *Annu. Phys. T. 1* **1976**, 145.
10. Gill, W. D. *J. Appl. Phys.* **1972**, *43*, 5033.
11. Weiser, G. *J. Appl. Phys.* **1972**, *43*, 5028.
12. Nakamura, T.; Ozaki, M.; Itaya, A.; Kusabayashi, S.; Mikawa, H. *Bull. Chem. Soc. Jpn.* **1975**, *48*, 1362.
13. Matsuoka, M.; Yodoshi, T.; Han, L.; Kitao, T. *Dyes and Pigments* **1988**, *9*, 343.
14. Lucki, R. *J. Polym. Photochem.* **1985**, *6*, 273.
15. Lim, H-S. Ph. D. Thesis, Osaka University 1989.
16. Bodea, C.; Silberg, I. *Adv. Heterocyc. Chem.* **1968**, *9*, 321.